

THE INTERNATIONAL RESEARCH GROUP ON WOOD PROTECTION  
Section 4 PROCESSES AND PROPERTIES

**Evaluation of the natural durability of reed (*Phragmites australis*)  
originating in the Fertö region (Hungary) against wood decay  
organisms as material for use in a sustainable motorway noise  
barrier.**

**M.T. Troya, F. Rubio, M.J. Prieto, D. Lorenzo, J.L. Fernández-Cabo, R. Schöftner**

Instituto Nacional de Investigación y Tecnología Agraria y Alimentaria (INIA)  
Centro de Investigación Forestal (CIFOR)  
Ctra. Coruña km. 7, 28040-Madrid  
Spain  
Facultad de Farmacia, Universidad San Pablo, Boadilla del Monte-Madrid Spain  
Polytechnic University, Madrid, Spain  
Functional Surfaces & Nanostructures, PROFACTOR GmbH, 4407 Steyr-Gleink (Austria)

Paper prepared for the 40<sup>th</sup> Annual Meeting  
Beijing, China  
24-28 May 2009

IRG SECRETARIAT  
Box 5609  
SE-114 86 Stockholm  
Sweden  
[www.irg-wp.com](http://www.irg-wp.com)

# Evaluation of the natural durability of reed (*Phragmites australis*) originating in the Fertö region (Hungary) against wood decay organisms as material for use in a sustainable motorway noise barrier

M.T. Troya<sup>1</sup>, F. Rubio<sup>2</sup>, M.J. Prieto<sup>1</sup>, D. Lorenzo<sup>1</sup>, J.L. Fernández-Cabo<sup>3</sup>, R. Schöftner<sup>4</sup>

<sup>1</sup> Centro de Investigación Forestal, Instituto Nacional de Investigación y Tecnología Agraria y Alimentaria, Ctra. Coruña km. 7, 28040-Madrid (Spain), troya@inia.es, mjprieto@inia.es

<sup>2</sup> Dpto. de Biología Celular, Bioquímica y Biología Molecular, Facultad de Farmacia, Universidad San Pablo, Urbanización Montepríncipe (Boadilla del Monte) (Madrid) (Spain), frubcre@ceu.es

<sup>3</sup> Polytechnic University of Madrid (Universidad Politécnica de Madrid), jose.fcabo@upm.es

<sup>4</sup> Functional Surfaces & Nanostructures, PROFACTOR GmbH, 4407 Steyr-Gleink (Austria), rainer.schoeftner@profactor.at

## ABSTRACT

This work presents the research carried out to determine the natural durability of reed from the Fertö region of Hungary against wood decay organisms. The final objective of this study is to obtain sufficient relevant data in order that the reed may be used as a constituent element in a viable and sustainable motorway noise barrier, which has been developed within the European research project, known by the acronym HOLIWOOD. The common reed grass (*Phragmites australis*, or *Phragmites communis*) is a large perennial grass of considerable size which grows in temperate and tropical wetland zones throughout the world. Its growth is expansive and it frequently invades wetlands where it competes with the native species and therefore requires regular removal so that an excess of organic material is not produced in the habitat. In addition, the invasion by this plant of polluted waters also appears to have a beneficial effect, so it can be used as a natural water purifier and thus has a potential use as a purification method for wetlands contaminated by agricultural practices. Due to the need for its periodic extraction its possible use as a construction material, although in a secondary role, gives it an added value for which further scientific study is required. In the absence of a reference Standard and being reed a lignocellulose material, the study of its natural durability has been based on the existing Standards for wood. The tests show that Hungarian reed has a high level of durability against some fungi and other wood decay organisms.

**Keywords:** Reed, sustainable noise barrier, durability, wood decay organisms.

## INTRODUCTION

The high cost involved in the construction and renovation of noise barriers makes the development of sustainable barriers necessary. In order to evaluate the foresaid barriers, it is necessary to make a Life Cycle Analysis (LCA). This work is being carried out within the HOLIWOOD project in accordance with ISO14040ff, (Caduff *et al.* 2005). The LCA provides important information for the selection of noise barriers as there is no reliable long term field data in existence available concerning the repositioning and maintenance of the aforementioned barriers (Morgan and Kay 2001, Ekici and Bougdah 2003). In any case it is clear that the reed has the initial advantage that it contains biogenic CO<sub>2</sub>.

Wood has been used in various ways in the existing barriers (Beilkircher *et al.* 2005a), even to the extent of being the only material used (Grgurevich *et al.* 2002, Boothby *et al.* 2001). The most common methods reduce its use to a structural one, other materials being added to provide the sound absorption. However, as wood is a biodegradable material, it requires treatment with various chemicals in order to lengthen its life in service and, due to the restrictions imposed by the European Directive on Biocides, this has resulted in wood being replaced by other materials.

The barrier designed in the HOLIWOOD project (Fig. 1) uses thermotreated timber (TMT), hardwood and softwood, as its structural support, therefore dispensing with the otherwise necessary chemical treatment. At present, there are no European Standards regarding TMT, although one is in the process of being devised (CEN/TC 175, TC 175 WI 00175118:2006). Mitteramskogler GMBH, a member of the HOLIWOOD project, is involved in its development, so that the heat treatment of the timber used in the barrier would be included in future Standards (Beikircher 2005b). The grading of the TMT has been considered within the project too (Widmann 2008).



Figure 1: Picture of the noise barrier in construction for the A22 motorway near Vienna.

However, the rational use of TMT requires the help of other materials, due as much to the need to improve the acoustic absorption qualities as to its cost. In the case of the barrier which has been designed, reed was selected as the complementary material. The barrier is basically formed with thermo-treated wood as the external structure - joists- with reed panels between them, which also improve the acoustic qualities. As an auxiliary material for the sound absorption requirement, 5cm thick bands of recycled rubber were added to the barrier (Fig. 1).

The acoustic barriers are required for a life in service of around 25 years and this needs the study of the natural durability of reed in the aforementioned project. There are few studies of the natural durability of this material (Haslam 1989ab, 1995, Bosman 1985). The results obtained in these investigations can not be extrapolated when the habitat changes because there is a large genetic variation and consequently their properties vary depending of the environment where the variety of reed grows (Haslam 1969, 1970, Chen *et al.* 2006, Zhu *et al.* 2003). Reeds originating from Hungary were specifically studied in this project, in particular those from the Fertö Reed Co, a member of the HOLIWOOD project.

At a general level, information on humidity must be taken into account as the existence and retention of humidity is fundamental for the fragility of the reed, because the way in which water is repelled or evaporated determines the life in service of the constructions and reed structures. Moreover, recent investigations based on the samples of 20 north facing and 20 south facing roofs in Denmark have improved the knowledge about long term vulnerability of the reed used as a roofing material (Anthony 1999). It has been

observed that the deterioration of the aforementioned roofs begins at the exposed surface and progressively affects the interior parts. Areas representative of the different states of decay are developed on the external reed covering. These areas move towards the interior as the roof deteriorates. It has been noted that the velocity at which deterioration occurs depends on the pitches of the roof, the deterioration being much greater in roofs with lower pitches. This issue has already been considered in the design process of the barrier, and the drainage of rainwater is immediate as there are no places where it can accumulate.

The selection of reed as part of a sound barrier has been supported by previous research which confirmed not only its effectiveness as a protective acoustic material (Jiménez-Espada *et al.* 2007), but also the possibility of it being a valid absorption material (Cookson *et al.* 2007). Mechanical trials were carried out which proved equally satisfactory (Fernandez-Cabo *et al.* 2008).

All this considered the aim of this work has been to study the durability of this reed type against the action of wood decay organisms (fungi and insects).

## EXPERIMENTAL METHODS

### Natural Durability of Reed against Wood Decay Fungi

#### **Materials**

In order to evaluate the natural durability of the reed, two types of test were carried out, one accelerated and another applying the corresponding European Standard against destroying Basidiomycetes and Ascomycetes, producers of white, brown and soft rots.

As test fungi has been used: *Coniophora puteana* (Shumacher ex Fries) Korsten, *Postia placenta* (Fries) Cooke Sensus J, Eriksson and *Gloeophyllum trabeum* (Persoon ex Fries) Murril for brown rot; *Trametes versicolor* (Linnaeus) Chalet for white rot and *Chaetomium globosum* Kunze, as representative of the fungi which produce soft rot.

The wood reference species used were: *Pinus sylvestris* L. for the fungi which cause the brown rot and *Fagus sylvatica* L. for those causing white and soft rot.

- In the accelerated tests, 9 reeds (30 mm long by 6mm in diameter), were used as specimen for each test fungus. Block tests (15 x 10 x 5 mm) of *P. sylvestris* were used as the reference species for the brown rot fungi, and *F. sylvatica* as the reference species for the white rot and soft rot fungi.
- In the test applying the current European Standard EN-350-1 (1995), groups of reeds of varying numbers and sizes were used depending on the type of rot:
  - For tests of brown and white rots were used:
    - Four bundles of reeds simulating woodblocks (50 x 25 x 15 mm) with 10 reeds per specimen for each test fungi.
    - Control block tests (50 x 25 x 15 mm) of *P. sylvestris* were used as the reference species for the fungi which cause brown rot and *F. sylvatica* as the reference species for the fungi which cause white rot.
  - For tests of the soil inhabiting microorganisms which cause soft rot:
    - Bundles of 6 reeds (100 mm long) were used.
    - Control block tests (100 x 10 x 5 mm) of *F. sylvatica* were used as the reference species.

## **Methods**

The specimens used in the tests were placed in an oven at 103°C to obtain the initial dry mass. They were subsequently sterilized and exposed to the corresponding fungi.

### Accelerated Tests

a) In the case of the Basidiomycetes, Petri dishes with pure cultures of test fungi which had previously been grown in a malt agar medium (1,5%, malt 3,0%) were used. Three pieces of reed and two control block tests of the reference woods were placed in each dish. The dishes were incubated in a culture chamber at 22°C and with 75% relative humidity for 45 days.

b) In the case of the soil inhabiting microorganisms causing soft rot, the specimens were buried in horticultural soil following European Standard ENV-807 (1993), and incubated at 28°C with 80% relative humidity for 16 weeks.

### Tests applying European Standards

For these tests the methodologies described in the European Standard EN-350 “Durability of wood and wood based products. Natural durability of solid wood” was applied. This means to follow the Standard EN-113 (1996) for white and brown rot fungi, and the ENV-807 (1993) for the soil inhabiting microorganisms producing soft rot.

After the corresponding incubation periods (16 weeks for EN-113 and 32 weeks for ENV-807) the block tests were removed and placed again in an oven at 103°C to obtain the final dry mass, and their weight losses.

## **Natural Durability of Reed against Wood Decay Insects**

### **Materials**

The subterranean termite species used in the test was *Reticulitermes grassei* Clément, while that of house longhorn beetle was *Hyloptrupes bajulus* L.

Specimens of reeds similar to those described for the fungi tests, and *P. sylvestris* L. (50 x 25 x 5 mm) as reference species, were used.

### **Methods**

#### Durability against termites

To evaluate the durability of the reed against termites, an accelerated test was used applying the methodology described by Nunes (1997) although slightly modified, using Petri dishes 60 mm in diameter. In each dish the reed specimens were added as cellulose material. As control Filter-Lab 12502 filter paper 42.5 mm in diameter was used as cellulose substrate. Fifteen termites were added to each dish, and then they were placed on the culture chamber at 28°C and 80% relative humidity during 4 weeks. The number of replicates was three.

#### Durability against house longhorn beetle

To determine this durability, 17 bundles made with 10 reeds each simulating block tests (50 x 25 x 15mm) were prepared. For the control, 6 Scots pine block tests were used. In three of them a hole to the middle of the block was perforated in the transversal section,

and in the remaining specimens a hole was drilled through all the length of the block in order to simulate the reed structure. Larvae in category two (masses in the range 50 to 150 mg) was placed in each block test, in accordance to the Standard EN-47. All the specimens were placed in the culturing chamber at 28°C with 80% relative humidity for 20 weeks. After this period the number of live larvae was counted.

The test can be considered valid if at least 70% of the larvae inserted into all the control test specimens survive.

## RESULTS AND DISCUSSION

Regarding the decay fungi, the results obtained from the accelerated test are shown in Table 1. Those corresponding to the application of Standard EN-113 in Table 2 (Fig. 2), and those obtained for soft rot in Table 3. In these tables the weight loss of reed compared with the reference wood species can be seen.

Table 1: Mean weight losses suffered by the studied materials in accelerated laboratory tests.

Fungi	Weight Loss [%]		
	Reed	<i>P. sylvestris</i>	<i>F. sylvatica</i>
<i>C. puteana</i>	0,87	30,34	-
<i>P. placenta</i>	3,66	11,52	-
<i>G. trabeum</i>	3,69	22,07	-
<i>T. versicolor</i>	5,90	-	34,40
<i>Ch. globosum</i>	15,31	-	18,46

Table 2: Mean weight losses suffered by the studied materials in accordance with EN-113, and its corresponding durability class.

Fungi	Weight Loss [%]			Durability Class
	Reed	<i>P. sylvestris</i>	<i>F. sylvatica</i>	
<i>C. puteana</i>	17,731	47,173	-	3 (moderately durable)
<i>P. placenta</i>	1,408	18,868	-	1 (very durable)
<i>G. trabeum</i>	14,450	41,950	-	3 (moderately durable)
<i>T. versicolor</i>	14,637	-	38,406	3 (moderately durable)

Table 3: Durability results of the soil inhabiting microorganisms test of reed in comparison with the beech.

Material	Weight loss [g]	Weight loss [%]	Natural Durability Class
Reed	0,306	5,273	3 (moderately durable)
<i>F. sylvatica</i>	0,546	17,53	5 (no durable)

As can be observed in Table 1, it appears that reed is durable against the brown and white rot fungi in the accelerated tests, but does not have the same resistance against soft rot fungi. When the corresponding European Standard was applied (Table 2), it is seen that reed exhibit a natural durability class 3 “moderately durable” against the

species of brown rot (*C puteana* and *G trabeum*), and against the species of white rot (*T versicolor*). However, against *P placenta*, which produces brown rot too, reed is shown to be a very durable material (durability class 1).

With respect to the results obtained by applying ENV-807 against soft rot, reed exhibits a class 3 natural durability (moderately durable).

In both Standards, the test reference wood species used are not durable (class 5).



Figure 2: Comparative appearance of the reed bundles and the corresponding controls in accordance with Standard EN-113.

Regarding durability against termites, the results obtained are shown in Table 4 where the number of surviving termites and the percentage weight loss incurred in each type of material are shown. As can be seen, reed is not completely durable against termites attack although the accelerated tests are not enough to get a final conclusion.

Table 4: Percentages of number of surviving termites and weight loss of materials studied.

Material	Survivors [%]	Weight loss [%]
Reed	46,6	6,47
Control (celulose)	86,6	13,81

The results obtained in relation to the durability of reed against *Hylotrupes bajulus* are shown in Table 5, where the number of surviving larvae, their percentage and the amount of sawdust in comparison with the Scots pine are shown. The appearance of the wood and of the reeds can be seen in Fig. 3.

As can be seen the percentage of surviving larvae in the reeds is very low (11,7%) compared with 100% in the controls. Moreover, as can be appreciated in Fig. 3, the larvae obtained from the reeds are either dead or of a comparatively smaller size than those found in the pine block tests. It must equally be noted that the amount of sawdust formed in the reeds is clearly less than in the reference specimens. With these results, it can be concluded that the reeds are durable.

Table 5: Percentages of number of surviving larvae of *Hylotrupes*, and the proportion of sawdust obtained

Material	No. of surviving larvae	Surviving larvae [%]	Sawdust [%]
Reed	2	11,7 %	1 %
<i>P. sylvestris</i>	6	100 %	100 %

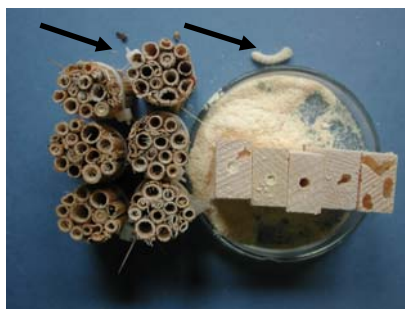


Figure 3: Comparative appearance of reed bundles with the corresponding pine blocks in accordance with EN-47 modified.

## CONCLUSIONS

The resistance of reed against fungi, applying the corresponding European Standards (EN-113 and ENV-807) show, depending on the type of fungi, durability levels which oscillate between class 3 (moderately durable) and class 1 (very durable). This confirms the previous results with accelerated tests that were somewhat better but within the same margins. Though the use of reed is not contemplated in the Standards used, the results clearly show a natural durability which is notably higher than the reference control wood species which in both cases are class 5 (not durable).

The tests against termites again show a superior performance with respect to the reference woods, but the reed was vulnerable to attack. Fortunately, this problem does not exist in cold countries such as those in northern and central Europe.

The results obtained in the trials against *Hylotrupes bajulus* are somewhat better than those against termites and again much better than the control woods.

The results shows a potential for exterior use when are compared with the control woods. For this reason, it is planned to monitor the acoustic panels that are being installed on the A22 motorway near Vienna. The construction design is, in any case, a crucial consideration in the prevention of water retention.

## Acknowledgements

The results presented were developed within the IP-SME project HOLIWOOD (Holistic implementation of European thermal treated hard wood in the sector of construction industry and noise protection by sustainable, knowledge-based and value added products). This Project is carried out with the financial support from the European Community within the Sixth Framework Program (NMP2-CT-2005-IP 011799-2). This publication reflects the authors view. The European Community is not liable for any use that may be made of the information contained therein.

## REFERENCES

Anthony, PA (1999): The macrofungi and decay of roofs thatched with water reed, *Phragmites communis*. *Mycol. Res.* **103**(10), 1346-1352.

Beikircher, W, Stötzel, M, Widmann, R, Oldham, D, Fernández-Cabo, JL, Schöftner, R (2005a): Detailed state of the art of Noise Protection Barrier Systems. *Deliverable D35 from the European project NO. NMP2-CT-2005-011799*, 70 pp. Project acronym: HOLIWOOD.

Beikircher, W, (Mitteramskogler GmbH) (2005b): Thermally Modified Timber by Mitteramskogler. *State of the Art. Report of WP: 1.1 and 1.4 of the HOLIWOOD project*.

Boothby, T E, Burroughs, C, Bernecker, CA, Manbeck, HB, Ritter, MA, Grgurevich, S, Cegelka, S, Hillbrich Lee, PD (2001): Design of Wood Highway Sound Barriers. *Forest Products Laboratory*. National Wood in Transportation Information Center Research. Paper FPL-RP-596. In cooperation with the United States Department of Transportation Federal Highway Administration.

Bosman, MTM (1985): Some effects of decay and weathering on the anatomical structure of the stem of *Phragmites communis*. *Trin. Ex Steud. Iawa Bulletin*, **6**,165-169.

Caduff, M, Althaus, HJ, Huber, H, Pristovnik, M (2005): Life Cycle Analysis (LCA) of the developed products (draft): *Deliverable D78 from the European project NO. NMP2-CT-2005-011799*. Project acronym: HOLIWOOD. 76 pp.

CEN/TC-175 (2006): Thermal Modified Timber. Definitions and Characteristics. TC 175 WI 00175118:2006.

Chen, KM, Wang, F, Wang, YH (2006): Anatomical and chemical characteristics of foliar vascular bundles in four reed ecotypes adapted to different habitats. *Flora*, **201**(7), 555-569.

Cookson, RD, Oldham, DJ, Egan, CA, Seiffert, G (2007): An experimental investigation of the potential of biomass materials as porous sound absorbers. *19th International Congress on Acoustics*. Madrid, 2-7 September.

Coops, H, Van der Velde, G (1996): Effects of waves on helophyte stands: mechanical characteristics of stems of *Phragmites communis* and *Scirpus lacustris*. *Aquatic Botany* **53**, 175-185.

EN-47 (1990): Determination of the toxic values against larvae of *Hylotrupes bajulus* (Linnaeus) - (Laboratory method). CEN.

EN-113 (1996): Test method for determining the protective effectiveness against wood destroying Basidiomycetes. Determination of the toxic values. CEN.

EN-350-1 (1995): Durability of wood and wood based products. Natural durability of solid wood. Part 1: guide to the principles of testing and classification of the natural durability of wood. CEN.

EN-350-2 (1995): Durability of wood and wood based products. Natural durability of solid wood. Part 2: guide to natural durability and treatability of selected wood species of importance in Europe. CEN.

ENV-807 (1993): Wood preservatives-Determination of the effectiveness against soft rotting micro-fungi and other soil inhabiting micro-organisms. CEN.

Ekici, I. and Bougdah, H.A. (2003): Review of research on environmental noise barriers. *Journal of Building Acoustics*, **10**, 289-323.

Fernández-Cabo, JL, Majano-Majano, A, González-Carabias, N, Troya, MT, Diaz-Sanchidrian, C, Jimenez-Espada, M, Bobadilla, I, Rubio, F, Prieto, MJ, Lorenzo, D (2008): Static calculations on the system and all components (draft). *Deliverable D47 from the European project NO. NMP2-CT-2005-011799*, 171 pp. Project acronym: HOLIWOOD.

Grgurevich, S, Boothby, T, Manbeck, H, Burroughs, C, Cegelka, S, Bernecker, C, Ritter, MA (2002): A comparative Study of wood highway sound barriers. *Forest Products Journal*, **52**(3), 35-43.

Haslam, SM (1969): Stem types of *Phragmites communis* Trin. *Annals of Botany*, **33**, 127-131.

Haslam, SM (1970): Variation of population type in *Phragmites communis* Trin. *Phragmites communis*. *Annals of Botany*, **34**, 147-158.

Haslam, SM (1989a): *Phragmites culm* strength and thatch breakdown: Some difficulties. *Landschaftsentwicklung und Umweltforschung, Technische Universität Berlin*, **71**, 58-77.

Haslam, SM (1989b): Early decay of *Phragmites* thatch: an outline of the problem. *Aquatic Botany*, **35**, 129-132.

Haslam, SM (1995): A discussion of the strength (durability) of thatching reed (*Phragmites australis*) in relation to habitat. *Reed research report*, Department of Plant Sciences, Cambridge. 56 pp.

Healy, MG, Rodgers, M, Mulqueen, J (2007): Treatment of dairy wastewater using constructed wetlands and intermittent sand filters. *Bioresource technology*, **98**(12), 2268-2281.

Jiménez-Espada, M, Díaz-Sanchidrian, C, Oldham, D, Fernandez-Cabo, JL, Pedrero, A (2007): The acoustical potential of reed panels for partitions in sustainable construction. *19th International Congress on Acoustics*. Madrid, 2-7 September 2007.

Massacci, A, Pietrini, F, Iannelli, MA (2001): Remediation of wetlands by *Phragmites australis* - The biological basis. *Minerva biotecnologica*, **13**(2), 135-140.

Morgan, SM, Kay, DH (2001): Selection of noise barrier material. Sustainability and environmental concerns in transportation. *Conference Information: 80th Annual Meeting of the Transportation-Research-Board*, Date: Jan, 2001, Washington D.C.

Widmann, R (2008): Allocation of Thermally Treated Structural Beech Timber to the European Strength- Classes and Relevant Grading and Quality Control Procedures. *Cost Action E53 Conference 29<sup>th</sup>-30th October 2008 in Delft, The Netherlands*

Zhu, XY, Wang, SM, Zhang, CL (2003): Composition and characteristic differences in photosynthetic membranes of two ecotypes of reed (*Phragmites communis* L.) from different habitats. *Photosynthetica*, **41**(1), 97-104.